

Generalized Néel-Brown theory for a temperature-dependent magnetic anisotropy

Martin Stier,¹ Alexander Neumann,² André Kobs,² Hans Peter Oepen,² and Michael Thorwart¹

¹*I. Institut für Theoretische Physik, Universität Hamburg, Jungiusstraße 9, 20355 Hamburg, Germany*

²*Institut für Angewandte Physik, Universität Hamburg, Jungiusstraße 11, 20355 Hamburg, Germany*

In order to switch its direction, a macroscopic magnetic moment of a superparamagnetic system has to overcome an energy barrier which is due to magnetic anisotropies in the material. The switching rate is usually described by a Néel-Brown-Arrhenius law, in which the energy barrier is a constant for a given temperature. However, magnetic anisotropies are in general depending on temperature. We take this temperature dependence into account and derive a generalized Néel-Brown theory for the switching rate. Importantly enough, this generalization has a tremendous effect on the physical interpretation of switching processes obtained in experiments on the basis of the conventional Arrhenius law. In particular, the assumption of a temperature-independent anisotropy may result in an overestimation of the attempt frequency by several orders of magnitude.

PACS numbers:

The development of devices for magnetic storage media faces several challenges in the ongoing miniaturization of information units. One of the fundamental physical problems is the so-called superparamagnetic limit. In the small scale limit the alignment of the ferromagnetic particle with a certain axis is no longer stable but affected by thermal energy. Despite similarities between para- and superparamagnetism, distinct differences exist. Quantum mechanics allows to describe paramagnetism rigorously with the magnetic field as a small perturbation. In superparamagnetism, the spins of a nanostructure are exchange coupled which causes a quasi-classical behavior with a large variety of possible energetically continuous states. Due to the large number of coupled spins, inferior energy contributions of the single spins become important (dipolar, spin-orbit effects). Such effects summarized as anisotropies compete with the thermal energy in a system of small spatial dimensions. The total energy of the nanomagnet reveals remarkable differences compared to the single moment case. In particular due to the competition with thermal energies, strongly changing behavior appears as function of temperature, for instance, blocking of the macrospin along a certain direction (easy axis of magnetization). In the latter situation, an energy barrier between the two degenerate states oriented parallel to the easy axis suppresses thermal switching. In case of an uniaxial system, the barrier height scales with the volume and strength of the anisotropy. At large enough temperature, the barrier can be overcome and the moment can flip back and forth. The motion of the magnetic moment in the potential well allows to define the so-called attempt frequency of the reversal process [1–3]. Besides a Boltzmann factor, scaling with the ratio of the total anisotropy energy and the thermal energy, the attempt frequency is in general considered as the only quantity which is influenced by temperature. In general, experiments are explained under the prerequisite of constant barrier heights to determine the magnetic anisotropy, thereby largely ignoring the extremely

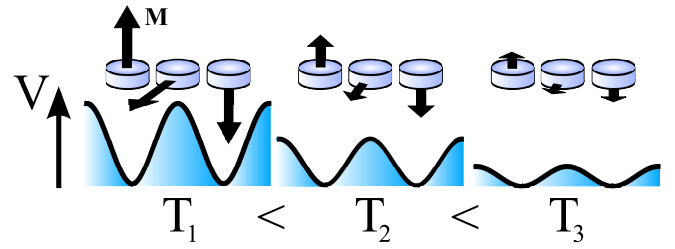


FIG. 1. (Color online) Sketch of magnetic potentials of superparamagnetic nanoislands for different temperatures with easy axis in the out-of-plane direction. To switch between the minima, the magnetization $\mathbf{M}$ has to overcome the anisotropy energy barrier which typically depends on $\mathbf{M}(T)$. With increasing temperature, both the magnetization and the energy barrier, are decreased.

varying attempt frequencies that are simultaneously obtained [4]. That unphysical results may arise has been pointed out in Ref. [5]. The authors have realized that the anisotropy may be temperature dependent and thus can lead to a wrong value of the attempt frequency. In general, it is well known that the anisotropy changes with temperature due to changes of microscopic lattice parameters, strain and others. In this Letter, we point out that besides the blocking temperature T_B , a second temperature scale becomes relevant in the macrospin description which is the ordering temperature T_C . So far, this fact has not been taken into account for the interpretation of experiments with superparamagnets. We show that for an appropriate interpretation of the temperature behavior of nanoparticles, temperature has to be considered with respect to the ordering temperature. In particular, we demonstrate that the finite ordering temperature has a strong impact on the switching dynamics of superparamagnets. We illustrate that experimentally determined prefactors [6–9] have to be reinterpreted particularly when the temperature scale of the measurements is comparable with the ordering temperature.

Microscopically a superparamagnetic system can be de-

scribed by the Heisenberg model

$$H = -J \sum_{\langle i,j \rangle} \mathbf{S}_i \cdot \mathbf{S}_j + H_{\text{aniso}}, \quad (1)$$

where the spins $\mathbf{S}_i$ tend to align parallel due to the exchange interaction of strength J in order to form a macroscopic magnetic moment. The exchange interaction itself is rotationally invariant and thus does not favor a certain direction for the resulting magnetic moment. However, superparamagnetic systems typically possess either intrinsic material symmetries or external ones such as a shape anisotropy. Then, distinct directions of the magnetic moment are preferred. To model this feature, a generic anisotropy term is introduced in Eq. (1). The specific form of the anisotropy has to be defined for the particular experimental situation.

We assume the magnetic system as large enough to form a macroscopic spin but still sufficiently small to avoid a separation into multiple magnetic domains. In this superparamagnetic limit, we can replace the collection of microscopic quantum spins by classical vectors $\mathbf{S}_i \rightarrow \mathbf{m}_i$ and assume a translationally invariant system ($\langle S_i^z \rangle \equiv \langle S^z \rangle \forall i$). Changing to magnetization as order parameter the uniaxial anisotropy is described by an energy density and the anisotropy part in Eq. (1) becomes

$$H_{\text{aniso}} = -KV \cos^2 \theta, \quad (2)$$

with θ being the angle which the magnetization encloses with the z-axis. The total Hamiltonian for a particle of volume V and $\mathbf{M}$ has two energy minima for $\mathbf{M} = \pm |\mathbf{M}| \mathbf{e}_z$. In order to reverse its direction, the total magnetic moment has to switch from one minimum to the other by surmounting the energy barrier $\Delta E = H_{\text{aniso}}(\theta = 90^\circ) - H_{\text{aniso}}(\theta = 0^\circ, 180^\circ) = KV$ while crossing the highest energy state at $\theta = 90^\circ$. The interaction part of Eq. (1) is irrelevant for determining the energy barrier as it is rotationally invariant and will only be considered implicitly as the mechanism causing the magnetic order. At finite temperature, the difference of the free energy $\Delta F(T) = \Delta E(T) - T\Delta S(T)$ determines the height of the switching barrier. However, we assume the entropy $S(T)$ does not change significantly by a rotation of the magnetization and set $T\Delta S \ll \Delta E$. For the discussion in the following, it is crucial to note that the anisotropy is related to the particle magnetization via a conventional power law $K = \tilde{K}[M(T)/M(0)]^\nu$ with the temperature dependent magnetization $M(T)$ and $M(0)$, $\tilde{K}$ the corresponding values at zero Kelvin [10–14]. For the sake of simplicity we consider the uniaxial anisotropy to be of dipolar origin. Then, the energy difference between hard and easy axis is given by $\Delta E = V\hat{N}M^2$ [15] with $\hat{N}$ stemming from the demagnetization tensor. Thus, we find

$$\Delta E(T) = V\hat{N}M(T)^2 \equiv K_0M(T)^2, \quad (3)$$

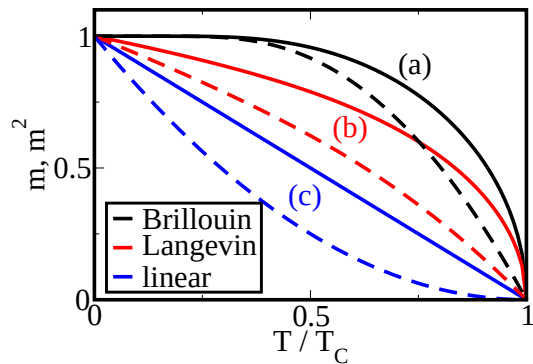


FIG. 2. (Color online) Temperature dependence of the magnetization $m = M(T)/M(0)$ (full lines) and its square m^2 (dashed lines) described by (a) the Brillouin function $B(S, T_C)$ for a spin $S = \frac{1}{2}$, (b) Langevin function $L(T_C)$ for a classical spin, and (c) a linear dependence $m(T) = 1 - T/T_C$. T_C denotes the Curie temperature of the system.

with $\Delta E(T)$ typically decreasing with increasing temperature, as it is sketched in Fig. 1.

We focus in this work on the consequences of a temperature-dependent anisotropy for the switching rate and thus investigate a model where the rate is given by a generalized Néel-Brown-Arrhenius law

$$f(T) = f_0 e^{-\frac{K_0 M(T)^2}{k_B T}}. \quad (4)$$

We fix the attempt frequency to $f_0 = 10^9 \text{ s}^{-1}$ and the anisotropy energy to $K_0 M(T=0)^2 = 1 \text{ eV}$ throughout this work. The conclusions below hold even for reasonable deviations from Eq. (4). For example, a different exponent ν in $M(T)^\nu$ may be absorbed in the actual temperature dependence of $M(T)$, while a (non-exponential) temperature dependence of the prefactor f_0 [2] is in first order negligible.

The actual magnetization of a physical system is affected by a multitude of material properties, such as intrinsic interactions or the finite sample size. While in ferromagnetic bulk samples the temperature dependence of the magnetization is typically well described by a Brillouin function, this is often not true in systems of reduced dimensions [13, 16, 17]. Thus, a general assumption of $M(T)$ cannot be made without explicit knowledge of the system. To illustrate that the explicit temperature-dependence of $M(T)$ has a major effect on the switching rate, we consider three different examples in this Letter: (a) the Brillouin function describes quantum spins in a bulk sample, (b) the Langevin function refers to a classical moment ($M \rightarrow \infty$), and (c) a linear dependence such that $M(T) = M(0)(1 - T/T_C)$ (with the Curie temperature T_C) as a possible variant of an unconventional magnetization curve which can be realized in magnetic nano-islands [11]. These functions and their squares are shown in Fig. 2.

In general, $M(T)$ decreases with increasing temperature

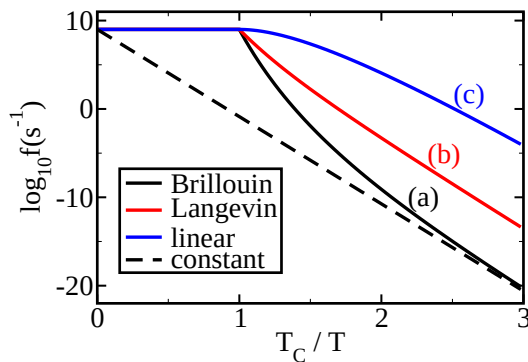


FIG. 3. (Color online) Decadic logarithm of the switching rate Eq. (4) for the temperature-dependent magnetizations shown in Fig. 2. Strong deviations from an Arrhenius law with a constant anisotropy $K_0 M(T)^2 \equiv K_0 M(0)^2$ (dashed line) appear even for $T \ll T_C$. Parameters are $f_0 = 10^9 \text{ s}^{-1}$ and $K_0 M(0)^2 = 1 \text{ eV}$.

and vanishes at the Curie temperature T_C which also holds for $\Delta E(T) \propto M(T)^2$. Thus, the system does not only switch faster with growing temperature due to an explicit increase of thermal fluctuations, but also due to a lower anisotropy barrier. This has a pronounced effect of the switching rate which is shown in Fig. 3. For convenience we use the decadic logarithm $\lg \equiv \log_{10}$ to directly determine the exponent y of the frequency according to $f = 10^y \text{ s}^{-1}$. Strong deviations from an Arrhenius law with a constant energy barrier are clearly visible.

These deviations are not captured by a linear adjustment of the Arrhenius law with a temperature shift $T \rightarrow T - T_0$, which yields to the Vogel-Fulcher law. Above T_C , this is obvious as the magnetization, and with it the energy barrier, vanishes. Close to T_C , the explicit values of $f(T \approx T_C)$ lose their physical meaning since the concept of a switching rate with a separation of time scales breaks down [3]. However, from the existence of a finite critical T_C with $\Delta E(T \geq T_C) \equiv 0$ and $f(T \geq T_C) \equiv f_0$, we have to conclude that such a system can hardly be described by a constant energy barrier as in this case, $f_{\Delta E=\text{const}}(T)$ would approach f_0 for $T \rightarrow \infty$ only. Thus, an accurate description of the switching rate requires the knowledge of the full temperature-dependent magnetization or even of the energy barrier at every temperature.

The generalized Néel-Brown theory of the switching rate has profound consequences for the interpretation of experimental data. In particular, the interpretation of the prefactor in terms of an attempt frequency has to be revisited. In real systems, it is not a realistic task to measure the switching rate $f(T)$ in the entire temperature regime from $T = 0$ to T_C . Usually, only a finite (and small) temperature interval $[T_{\min}, T_{\max}]$, with $\Delta T = T_{\max} - T_{\min} \approx 30 \dots 50 \text{ K}$ [7, 8] is experimentally accessible. Outside of this range, the switching is either too fast to be observable with present day tools or

too slow to be measured in a reasonable time. In fact, ΔT is usually small enough such that the magnetization does not significantly change with temperature and the switching rate appears linearly depending on T^{-1} in this interval. Thus, it is tempting to fit the results to a linear function

$$\lg f = \lg f_0^{\text{fit}} - \lg(e) \frac{K_0^{\text{fit}}}{k_B T} \quad (5)$$

and to determine f_0 and K_0 . However, the interpretation of the results for the fitted parameters f_0^{fit} and K_0^{fit} can actually be misleading. This is illustrated for a simple analytical example for which we assume for once a temperature-dependent magnetization $M(T) = M(0)\sqrt{1 - T/T_C}$. The switching rate resulting from Eq. (4) is now given by $\lg f = -\lg f_0^{\text{fit}} - \lg(e)(K_0 M(0)^2)/(k_B T)$ with $\lg f_0^{\text{fit}} = \lg f_0 + \lg(e)(K_0 M(0)^2)/(k_B T_C)$. This equation is in fact linearly depending on $1/T$ and would actually yield the result for $K_0^{\text{fit}} = K_0 M(0)^2$. However, more importantly, the exponent of the fitted prefactor (which is often interpreted as the attempt frequency) differs from the physical one by $\lg(e)K_0 M(0)^2/(k_B T_C)$. This difference can be very pronounced and, e.g., is for $f_0 = 10^9 \text{ s}^{-1}$ and $K_0 M^2(0) = 1 \text{ eV}$ given by $\lg f_0^{\text{fit}} \approx \lg f_0 + \frac{5000 \text{ K}}{T_C}$. Hence, the attempt frequency $f_0 = 10^y$ is in this case overestimated by five orders of magnitude for a typical $T_C = 1000 \text{ K}$.

For the three cases of $M(T)$ used above, also the deviation of the prefactor becomes now temperature dependent (this is not the case for the simplified model used in the previous paragraph). To show that this effect can be very pronounced, we use the same model parameters as above and numerically perform linear fits according to Eq. (5) in a small temperature interval $T \in [T^{\text{fit}} - T_C/200, T^{\text{fit}}]$. The results are shown in Fig. 4. The linear fits in general overestimate f_0 by several orders of magnitude. Interpreted as attempt frequencies, such linear fits yield to unrealistically large values reported in the analysis of experimental data on the basis of an Arrhenius or a Vogel-Fulcher law [6–9]. Naturally, the quality of the fit with respect to f_0 is the better, the less the magnetization depends on T in the respective window used for the fitting. Then, the magnetization is well approximated by the constant K_0^{fit} . For a Brillouin function, the (squared) magnetization varies less at lower temperatures (cf. Fig. 2). Thus, the best fits are achieved close to zero temperature. On the contrary, $m(T)^2 = [1 - (T/T_C)]^2$ changes the least close to the Curie temperature, which is also reflected in Fig. 4. Obviously, fits with the assumption of a constant energy barrier cannot deliver reliable results for K_0 , when $\Delta E(T)$ is actually changing with T . Even though K_0 probably is not misdetermined by orders of magnitude as it is fitted directly (and not its logarithm at $T \rightarrow \infty$ as for f_0), this correction of the barrier height has to be taken into account as well.

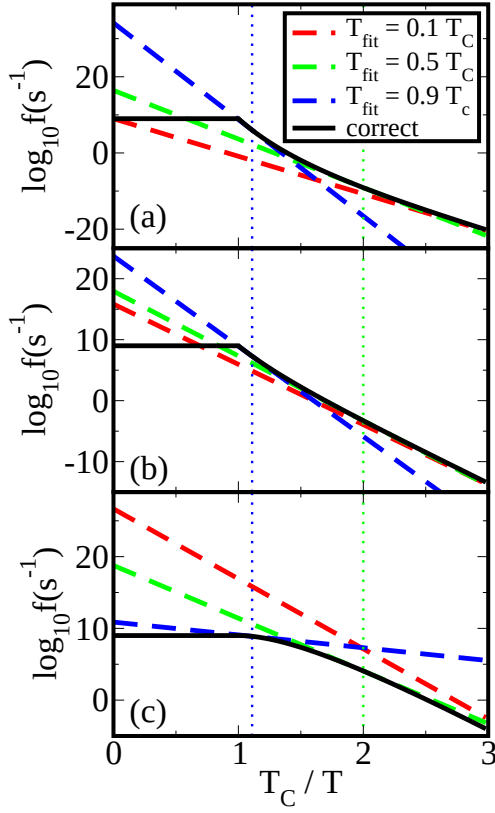


FIG. 4. (Color online) Linear fits (dashed lines) to the switching rate $\lg f = \lg f_0 - \lg(e)K_0 M(T)^2 / (k_B T)$ (full line), performed in a finite temperature interval around the given T_{fit} indicated by the vertical dotted lines (except for $T_{\text{fit}} = 0.1T_C$ which lies out of bounds) for (a) a Brillouin function for $S = \frac{1}{2}$, (b) a Langevin function, and (c) a linear dependence (cf. Fig. 2). The exponents of f_0^{fit} follow for $T_C/T \rightarrow 0$. Clearly, they can differ from the original f_0 by several orders of magnitude. The parameters are $f_0 = 10^9 \text{ s}^{-1}$, $K_0/M(0)^2 = 1 \text{ eV}$ and $T_C = 500 \text{ K}$.

The important consequences of a finite temperature window for the exponent of the fitted prefactor are illustrated in more detail in Fig. 5. We vary the position of the temperature window used for the fits and also the Curie temperature. In general, the regions for the optimal temperature T^{fit} are confirmed. An almost temperature-independent magnetization yields a well fitting attempt frequency $f_0^{\text{fit}} \approx f_0 = 10^9 \text{ s}^{-1}$. Everywhere else, it is significantly overestimated. What is more, the lower the Curie temperature is, the worse are the fitted results, which can be again traced back to the temperature dependence of $M(T)$. As the derivative $\partial_{\tilde{T}} M^2(\tilde{T})$ with respect to $\tilde{T} = T/T_C$ remains constant for all T_C for the three cases treated here, the derivative $\partial_T M^2(\tilde{T}) = T_C^{-1} \partial_{\tilde{T}} M^2(\tilde{T})$ is proportional to the inverse Curie temperature. Thus, we find a larger deviation for a lower T_C . This is important, since superparamagnetic phenomena are typically investigated for very small samples where the Curie temperature may be notably smaller

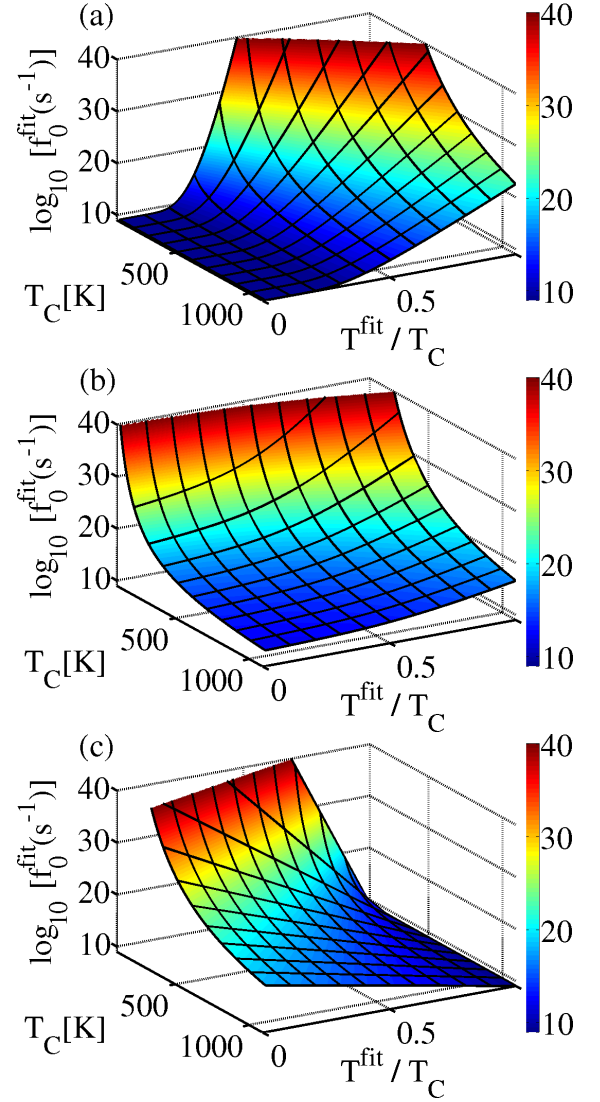


FIG. 5. (Color online) Fitted exponent of the attempt frequency. The magnetization is calculated by (a) a Brillouin function for $S = \frac{1}{2}$, (b) the Langevin function (classical magnetic moment) and (c) by a linear approach (cf. Fig. 2). The correct exponent would be $\lg f_0(\text{s}^{-1}) = 9$.

than in a bulk sample [18].

In this work we have shown that a temperature-dependent magnetic anisotropy in a superparamagnetic system can give rise to significant corrections to the standard Néel-Brown-Arrhenius law. For a correct interpretation of the parameters, the energy barrier for the switching of magnetic moment has to be based on a temperature-dependent magnetic anisotropy even in a simple model. This generates considerable corrections to the Arrhenius law. In particular the prefactor can no longer be determined in general by a fit of measured data on the basis of a temperature-independent anisotropy. Even if the fit appears plausible in a given finite temperature range, the attempt frequency can be misdetermined

by several orders of magnitude.

We acknowledge support from the DFG Sonderforschungsbereich 668 “Magnetismus vom Einzelatom zur Nanostruktur”.

-
- [1] H. Kramers, *Physica* **7**, 284 (1940).
 - [2] W. T. Coffey and Y. P. Kalmykov, *J. Appl. Phys.* **112**, 121301 (2012).
 - [3] P. Hänggi, P. Talkner, and M. Borkovec, *Rev. Mod. Phys.* **62**, 251 (1990).
 - [4] J. Dormann, D. Fiorani, and E. Tronc, *J. Magn. Magn. Mater.* **202**, 251 (1999).
 - [5] F. Wiekhorst, E. Shevchenko, H. Weller, and J. Kötzler, *Phys. Rev. B* **67**, 224416 (2003).
 - [6] M. Tadic, S. Kralj, M. Jagodic, D. Hanzel, and D. Makovec, *Appl. Surf. Sci.* **322**, 255 (2014).
 - [7] A. Neumann, *Magnetisierungsverhalten einzelner ferromagnetischer Nanostrukturen*, Ph.D. thesis, Universität Hamburg (2014).
 - [8] S. Krause, G. Herzog, T. Stapelfeldt, L. Berbil-Bautista, M. Bode, E. Vedmedenko, and R. Wiesendanger, *Phys. Rev. Lett.* **103**, 127202 (2009).
 - [9] R. Tackett, J. Parsons, B. Machado, S. Gaytan, L. Murr, and C. Botez, *Nanotechnology* **21**, 365703 (2010).
 - [10] O. N. Mryasov, U. Nowak, K. Y. Guslienko, and R. W. Chantrell, *Europhys. Lett.* **69**, 805 (2005).
 - [11] U. Nowak, O. N. Mryasov, R. Wieser, K. Guslienko, and R. W. Chantrell, *Phys. Rev. B* **72**, 172410 (2005).
 - [12] D. Böttcher, A. Ernst, and J. Henk, *J. of Phys.: Cond. Matt.* **23**, 296003 (2011).
 - [13] M. Farle, *Rep. Prog. Phys.* **61**, 755 (1998).
 - [14] H. Callen and E. Callen, *J. Phys. Chem. Solids* **27**, 1271 (1966).
 - [15] J. Dubowik, *Phys. Rev. B* **54**, 1088 (1996).
 - [16] J. Pierce, M. Torija, Z. Gai, J. Shi, T. Schulthess, G. Farnan, J. Wendelken, E. Plummer, and J. Shen, *Phys. Rev. Lett.* **92**, 237201 (2004).
 - [17] U. Gradmann, *Appl. Phys.* **3**, 161 (1974).
 - [18] C. Schneider, P. Bressler, P. Schuster, J. Kirschner, J. De Miguel, and R. Miranda, *Phys. Rev. Lett.* **64**, 1059 (1990).